arXiv:1303.3850v1 [cond-mat.str-el] 15 Mar 2013

Unconventional Magnetic Ground State in $Yb_2Ti_2O_7$

R. M. D'Ortenzio,[1, *] H. A. Dabkowska,[2] S. R. Dunsiger,[3] B. D. Gaulin,[1, 2, 4]
M. J. P. Gingras,[4, 5, 6] T. Goko,[7] J. B. Kycia,[5] L. Liu,[7] T. Medina,[1] T. J. Munsie,[1]
D. Pomaranski,[5] K. A. Ross,[8, 9] Y. J. Uemura,[7] T. J. Williams,[1] and G. M. Luke[1, 4]

[1] *Department of Physics and Astronomy, McMaster University,*
1280 Main St. W., Hamilton, ON, Canada, L8S 4M1
[2] *Brockhouse Institute for Materials Research, McMaster University, Hamilton, Ontario L8S 4M1, Canada*
[3] *Physik-Department E21, Technische Universitat Munchen, D-85748 Garching, Germany*
[4] *Canadian Institute for Advanced Research, Toronto, Ontario, Canada, M5G 1Z8*
[5] *Department of Physics and Astronomy, University of Waterloo, Waterloo, ON N2L 3G1, Canada*
[6] *Perimeter Institute for Theoretical Physics, 31 Caroline North, Waterloo, Ontario, N2L-2Y5, Canada*
[7] *Department of Physics, Columbia University, New York, New York 10027, USA*
[8] *Institute for Quantum Matter and Department of Physics and Astronomy,*
Johns Hopkins University, Baltimore, Maryland 21218, USA
[9] *NIST Center for Neutron Research, National Institute of Standards and Technology, Gaithersburg, Maryland 20899, USA*

(Dated: March 18, 2013)

We report low temperature specific heat and muon spin relaxation/rotation (μSR) measurements on both polycrystalline and single crystal samples of the pyrochlore magnet $Yb_2Ti_2O_7$. This system is believed to possess a spin Hamiltonian supporting a Quantum Spin Ice (QSI) ground state and to display sample variation in its low temperature heat capacity. Our two samples exhibit extremes of this sample variation, yet our μSR measurements indicate a similar disordered low temperature state down to 16 mK in both. We report little temperature dependence to the spin relaxation and no evidence for ferromagnetic order, in contrast to recent reports by Chang *et al.* (Nat. Comm. **3**, 992 (2012)). Transverse field (TF) μSR measurements show changes in the temperature dependence of the muon Knight shift which coincide with heat capacity anomalies. We are therefore led to propose that $Yb_2Ti_2O_7$ enters a hidden order ground state below $T_c \sim 265$ mK where the nature of the ordered state is unknown but distinct from simple long range order.

Rare earth titanates of the form $R_2Ti_2O_7$ (R is a trivalent magnetic rare earth ion and the Ti is non−magnetic) provide an excellent vehicle for the study of geometric magnetic frustration. The R sites within the cubic pyrochlore structure, with space group $Fd\bar{3}m$, reside on a network of corner sharing tetrahedra, with a high propensity towards frustrated magnetic interactions leading to a wide range of exotic low temperature magnetic states [1]. For example, classical spin ice materials have been theoretically proposed to exhibit monopole-like quasiparticle excitations [2].

Spin ices such as $Dy_2Ti_2O_7$ have been extensively studied and are relatively well understood [1]. Recently, a new direction that has received much interest is that of "quantum spin ice", where quantum fluctuations may elevate the classical spin liquid state of spin ice to a full blown quantum spin liquid. A possible candidate for a quantum spin ice is $Yb_2Ti_2O_7$, which does not exhibit the gradual spin freezing and residual low-temperature entropy of a classical spin ice [3]. However, the nature of its ground state is currently under much debate, with some recent experiments reporting a ferromagnetic low temperature state [4, 5], while others show a dynamic ground state with no long range order [6–9]. Despite this, the microscopic Hamiltonian for $Yb_2Ti_2O_7$ appears well described by a pseudospin−1/2 quantum spin ice model [3, 10, 11].

Previous zero field (ZF) μSR [6, 12] performed on polycrystalline $Yb_2Ti_2O_7$ showed no evidence of long range magnetic order below the sharp specific heat transition at ∼240 mK, rather they reported a Yb^{3+} spin fluctuation rate drop of approximately 4 orders of magnitude [13]. Mössbauer absorption spectra by the same group also indicated a first order magnetic transition, but could not give information about the microscopic nature of the ground state. Neutron scattering experiments show evidence for both an ordered ferromagnetic ground state [4, 5], and a dynamic magnetic ground state, with only short range (3D) spin correlations [7, 9]. Ross *et al.* [7, 9] report rods of magnetic scattering along the ⟨111⟩ directions, characteristic of short range two−dimensional (2D) correlations above 400 mK. Below 400 mK, the rods begin to coalesce and build up intensity near the $\boldsymbol{Q} = (1, 1, 1)$ Bragg peak, interpreted [10] as a cross-over to short range three-dimensional (3D) magnetic correlations, but clearly lacking long range order. Inelastic neutron scattering at 30 mK in these same studies shows only diffuse quasielastic scattering, and no evidence of sharp spin waves, again consistent with a dynamic disordered ground state. In contrast with Ref. [7], Chang's polarized neutron scattering results [4] show suppression of the ⟨111⟩ scattering rods into full magnetic Bragg peaks in a first order manner below T∼210 mK.

Recent evidence suggests that, like other geometrically frustrated magnets such as $Tb_2Ti_2O_7$ [14], $Yb_2Ti_2O_7$'s ground state may be sensitive to small amounts of quenched disorder and non-stoichiometry at the ∼1%

level, with several reports of sample variation of the strong heat capacity anomaly near ∼260 mK and below [7, 15, 16]. Variation of the heat capacity is observed between samples, both poly− and single−crystalline, and the largest heat capacity anomaly appearing at the highest temperature could be taken as a figure of merit for the sample quality. To date, this anomaly is seen to be sharpest in polycrystalline samples that were prepared by the method outlined in Ref. [15].

Neutron diffraction studies [15] have shown that a single crystal of $Yb_2Ti_2O_7$ grown using the optical floating zone technique is weakly “stuffed”, with stoichiometry $Yb_2(Ti_{2-x}Yb_x)O_{7-x/2}$ where x ∼0.046, or 2.3% extra Yb^{3+} ions reside on the nonmagnetic Ti^{4+} sublattice. Meanwhile, polycrystalline samples prepared by the method in Ref. [15] are not stuffed (x=0). These defects are proposed [15] to contribute to the variation in magnetic ground state properties, and therefore the variation in the heat capacity observed in different samples.

In this letter, we study two samples of $Yb_2Ti_2O_7$ with very different low temperature heat capacities, shown in Fig. 1. One is a polycrystalline sample with a sharp, large heat capacity anomaly at relatively high T_c∼265 mK, while the other is a single crystal sample which displays a broad anomaly at T_c∼185 mK, with a peak amplitude 20 times smaller than that of the polycrystalline sample. For comparison, we also show the specific heat measurements reported by Chang *et al.* for the single crystal used in their neutron study [4], Dalmas de Réotier *et al.*’s polycrystalline sample used in a previous μSR study [6] and Ross *et al.*’s polycrystal used in Ref. [7]. Based on our specific heat data, we would expect our single crystal to have a relatively high degree of stuffing as the specific heat peak is pushed down to ∼185 mK. Our polycrystalline sample shows a sharp temperature peak, from which we infer that it should be closer to balanced stoichiometry ($x \approx 0$). Remarkably, the μSR measurements we report show little difference between the two samples at low temperatures, and both the single crystal and our high quality polycrystalline sample are shown to remain disordered and dynamic to the lowest temperatures measured.

We prepared polycrystalline pellets of $Yb_2Ti_2O_7$ by mixing stoichiometric quantities of Yb_2O_3 and TiO_2, isotropically pressing at 60 MPa then sintering at 1200 °C for 24 hours. We then grew single crystal $Yb_2Ti_2O_7$ from some of the polycrystalline material using the optical floating zone crystal growth method in 2 ATM of O_2 as described in [17]. SQUID measurements of the dc-magnetization above 2 K confirm Curie-Weiss behavior with overall weak ferromagnetic interactions, Θ_{CW}=0.4 K, similar to values reported by previous studies [18, 19].

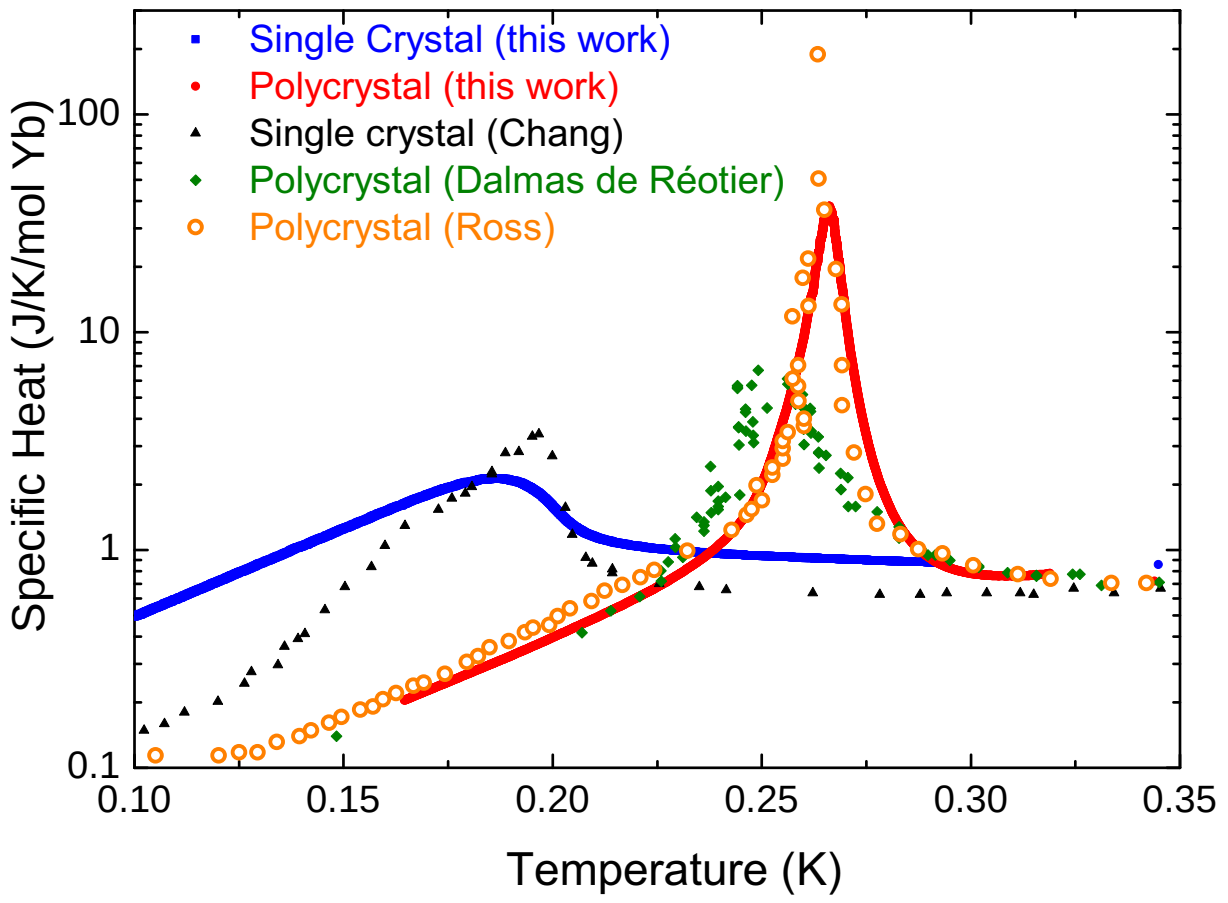

FIG. 1. Low T specific heat measurements of $Yb_2Ti_2O_7$ on a semi−logarithmic scale. The red and blue curves represent samples used for this work. Our polycrystalline sample exhibits a sharp transition at ∼265 mK, and our single crystal shows a broad peak at ∼185 mK. The black data is taken from Chang et al.’s [4] single crystal, and the green is the sample [13] used for Hodges et al.’s μSR measurements. The orange points are taken from Ross et al [7].

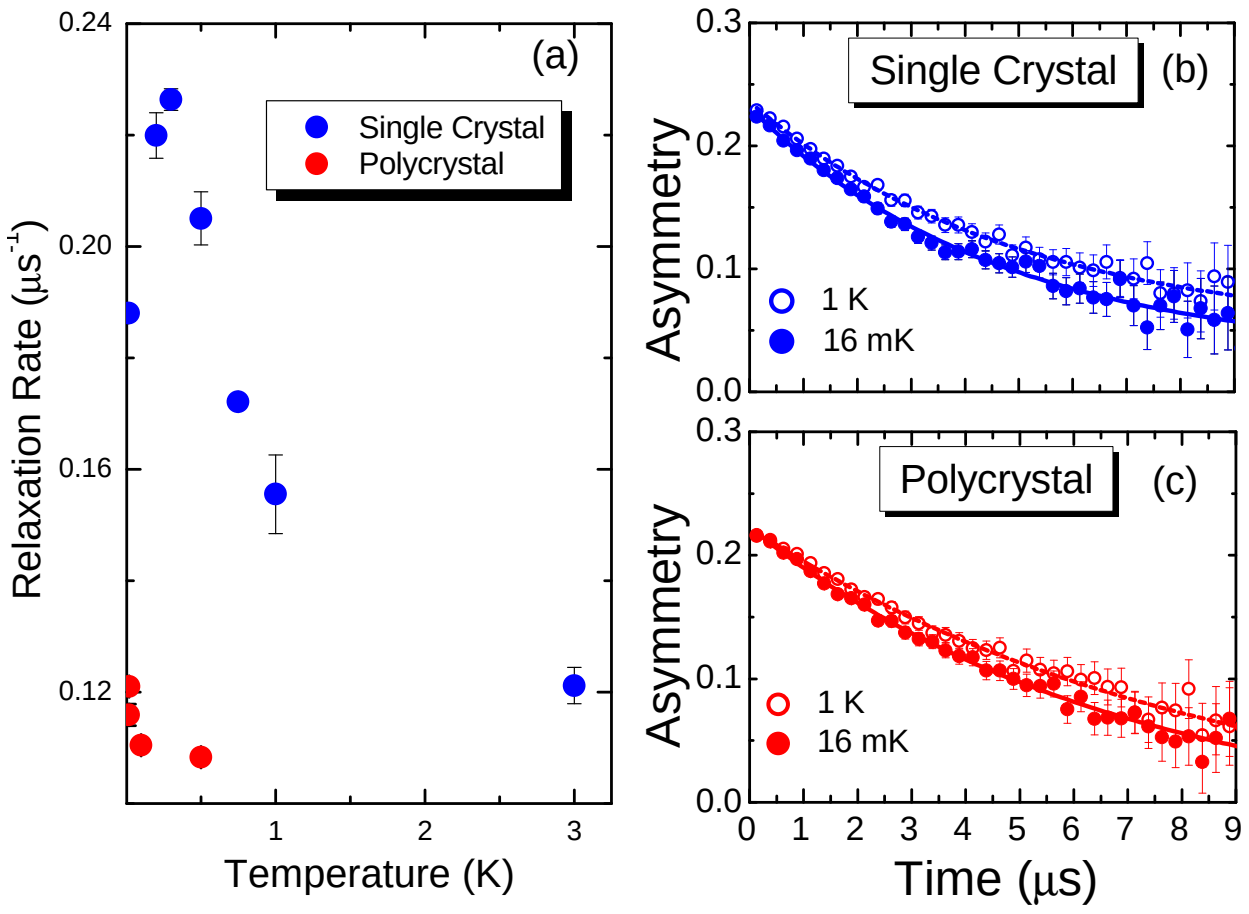

FIG. 2. A comparison of the weak LF (less than 0.5 mT) data for polycrystalline and single crystal $Yb_2Ti_2O_7$. Asymmetry spectra (shown in (b) and (c)) were fit with a single exponential decay with a globally fixed asymmetry for all T. Plot (a) shows the temperature dependence of the relaxation rate.

Weak longitudinal field (LF) μSR spectra are shown for T=1 K and 16 mK in Fig. 2 for both single crystal and polycrystalline samples. Calibration spectra using transverse counters show that the applied field is H≤0.5 mT. We confirmed that the longitudinal relaxation rate did not vary with the size of the weak applied field (up to at least ∼2 mT) indicating that the small field does not affect the dynamics of the Yb^{3+} moments, although it does serve to decouple any static nuclear dipole relaxation from any stray muons landing in the cryostat tails or sample holder [20].

We find that the entire muon polarization signal relaxes with a simple exponential decay and a weak relaxation rate that is only slightly temperature dependent, as shown in Fig. 2. No oscillatory component or rapid relaxation that would be observed from an ordered state is present down to 16 mK for either sample. The random orientations of crystallites in the polycrystal and the cubic symmetry giving three equivalent $\langle 111 \rangle$ directions in the single crystal preclude the possibility of a static local field soley along the initial muon polarization direction (where muon precession would not be observed) [21]. In marked contrast to the results presented in [6], we observe no fast relaxing component for either of our samples at any temperature, including below the transitions observed in the specific heat. This behavior allows us to conclude that the Yb^{3+} spins are in the fast fluctuating (narrowing) regime, with an absence of long range magnetic order or even static internal magnetic fields such as would be present in a spin glass system at low temperature. The relaxation rate does increase somewhat with decreasing temperature, indicating a gradual slowing down of Yb^{3+} spin fluctuations; however they remain rapidly fluctuating down to 16 mK.

To further characterize the Yb^{3+} spin system, we performed transverse field (TF) μSR measurements to probe the local spin susceptibility, applying H=50 mT perpendicular to the initial muon spin polarization, which was rotated 90° relative to the LF measurements. For the single crystal $Yb_2Ti_2O_7$, the field was applied parallel to [111] . H=50 mT is small enough not to induce a magnetically ordered state along [110], and likely also [111] [7, 9]. Fig. 3 shows Fourier transforms of time spectra measured at T=50 mK, which exhibit a number of resolved lines for each sample. The positively charged muon's site in materials is determined by electrostatic interactions, with muons in $Yb_2Ti_2O_7$ most likely to reside near O^{2-} ions [20]. There are two crystallographically inequivalent O^{2-} ions in the pyrochlore structure, both of which could provide muon sites. The application of an external magnetic field along a specific (in this case a [111]) axis makes several crystallographically equivalent sites magnetically inequivalent and can therefore increase the multiplicity of muon precession frequencies. The splitting of each line from the frequency corresponding to the applied field reflects the local (anisotropic) susceptibility of that particular muon site. The polycrystalline sample exhibits fewer lines, though they are broader in frequency as a result of the powder averaging of the anisotropic shifts of different crystallographic sites. After examining the Fourier transforms we chose to fit the time spectra to Eq. 1 with $n = 3$ (polycrystal) and $n = 4$ (single crystal), fixing the amplitudes of the individual components at all temperatures for each sample to values obtained from simultaneous global fits over a range of temperatures. Typical fits are shown in the insets of Fig. 4 (a) and (b) for the polycrystal and single crystal samples respectively.

$$A(t) = \sum_{i=1}^{n} A_i e^{-\sigma_i^2 t^2} \cos(\omega_i t + \varphi) \tag{1}$$

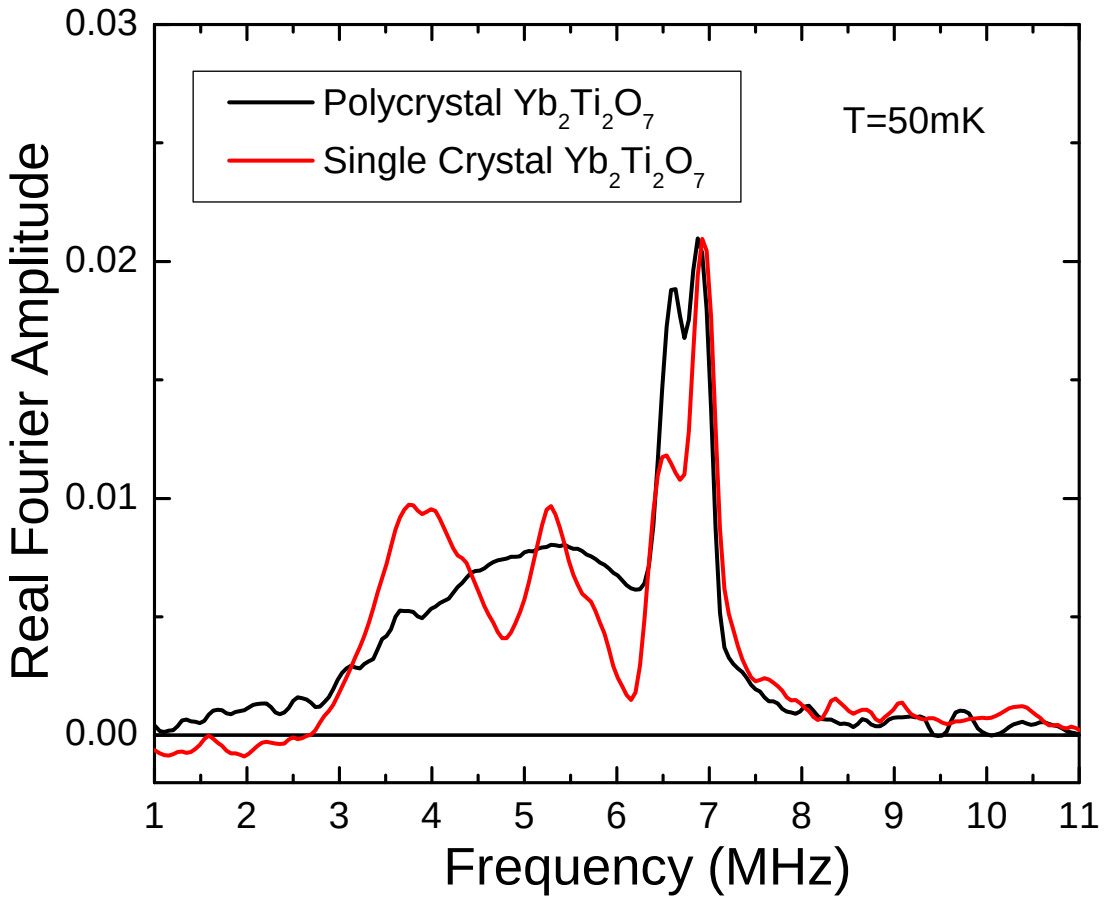

FIG. 3. Fourier Transform of μSR asymmetry spectra in a transverse field of 50 mT at T=50 mK. The single crystal $Yb_2Ti_2O_7$ shows 4 resolvable frequencies (red) and the polycrystalline $Yb_2Ti_2O_7$ shows three (black). This motivates $n = 4$ for the single crystal and $n = 3$ in the polycrystalline $Yb_2Ti_2O_7$ for Eq. (1). The sharp signal at approximately 7 MHz for both samples reflects the precession of the muons in the Ag cryostat tails.

We show the results of this analysis for the frequencies of each component in Fig. 4. The highest frequency component (labeled in grey) for each sample exhibits no temperature dependence. We ascribe this signal to muons landing in the silver sample holder which provides a useful reference signal for determining the muon Knight shift. The frequencies originating in the samples all show a strong temperature dependence as shown in Fig 4. We parametrized the Knight shifts of these signals referenced to the silver signal by fitting them to a Curie-Weiss temperature dependence in the temperature range 400 mK $< T <$ 3.5 K. We used a common "Curie-Weiss temperature" (T^{μ}_{CW}) for each signal which was allowed to vary between samples. The resulting frequencies obtained from these fits of the Knight shifts are indicated by the black solid lines in Fig. 4.; for both samples $T^{\mu}_{\mathrm{CW}} = -1.3 \pm 0.5$ K, which is considerably below the value (Θ_{CW}=+0.4 K) we obtain at higher temperatures (above 2 K) in dc-magnetization. For both samples we see a strong deviation from this parametrized Curie−Weiss behavior below the temperature corresponding to the onset of the specific heat phase transition, indicated by arrows in Fig. 4. This deviation indicates that there is a marked change in the muon Knight shift (which reflects the local spin susceptibility and Yb^{3+}-muon hyperfine coupling) onsetting at about the thermodynamic phase transition and that this occurs in both samples.

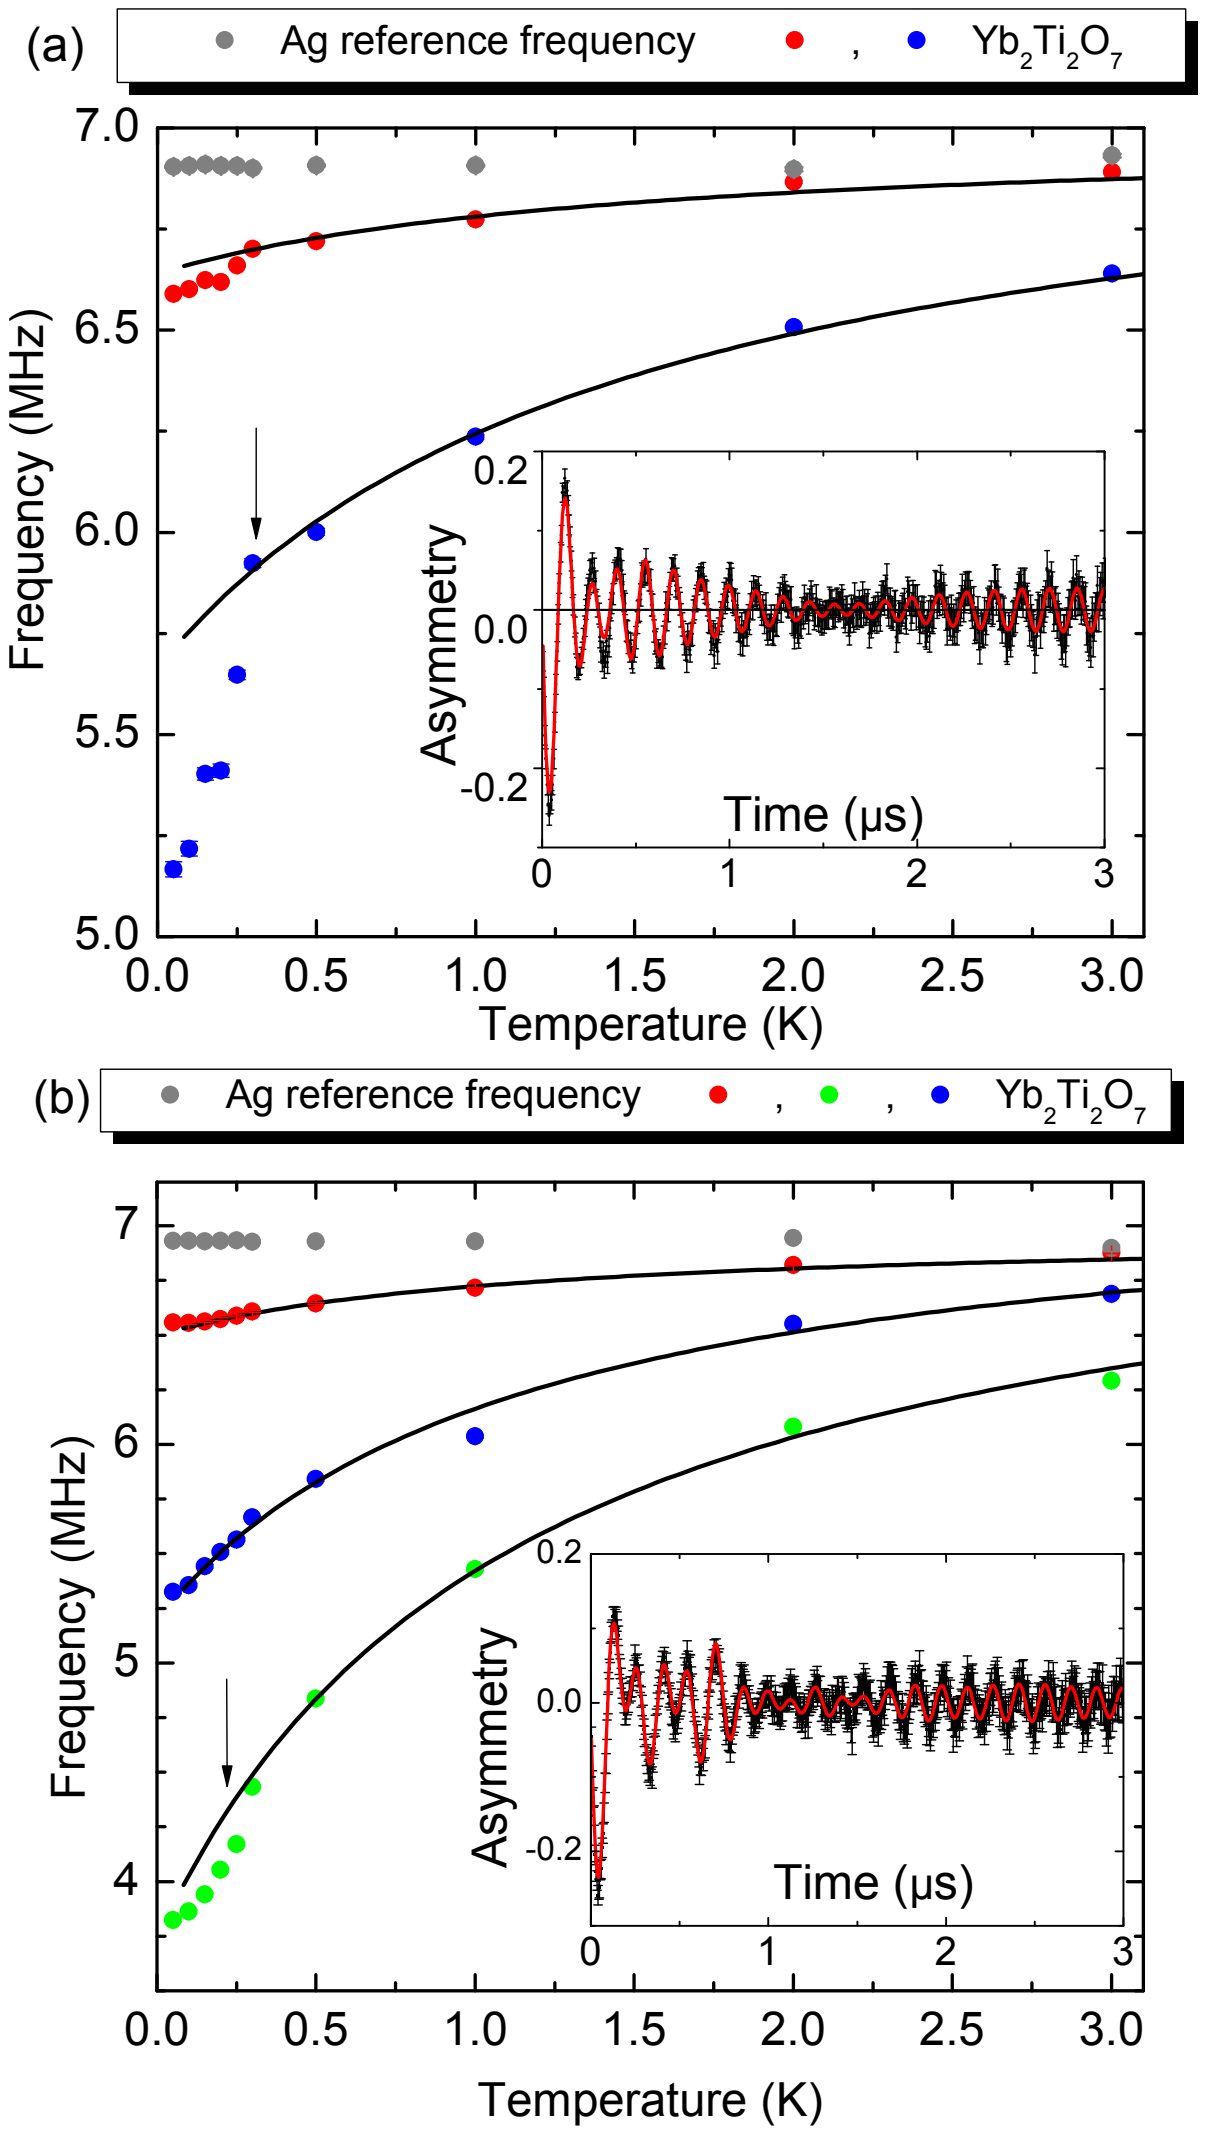

FIG. 4. The Yb^{3+} spin susceptibility characterized by TF= 50 mT μSR measurements of (a) polycrystalline and (b) single crystal $Yb_2Ti_2O_7$. For the single crystal $Yb_2Ti_2O_7$ the initial muon polarization points perpendicular to the TF field which was applied parallel to [111]. There are two distinct muon signals from the polycrystalline sample, and three from the single crystal sample. The arrows show the approximate temperature of the onset of the transition observed in the specific heat. The solid black lines represent Curie−Weiss fits, as described in the text. The insets show asymmetry spectra (black) and fit to Eq.1 (red).

The similarities of our data between the polycrystalline and single crystal samples is surprising considering their very different specific heat signatures indicating a wide range of stuffing [15]. It is also surprising that we see no evidence for the dramatic first-order-like change in the spin fluctuation rate that was previously reported [6]. This difference is apparent in the raw data and is evidence of a sample dependence between those studied by Hodges *et al.* and this work which must go beyond the differences in stuffing between our polycrystal and single crystal samples. Our results suggest that from a local microscopic point of view, the magnetic ground state is to a large extent insensitive to to some aspects of sample variation, and that a sharp specific heat transition does not signify magnetic order.

Our weak LF measurements, shown in Fig. 2 exhibit a weakly temperature dependent spin fluctuation rate to the lowest temperatures studied. Many frustrated pyrochlore systems exhibit a substantial, largely temperature independent LF/ZF relaxation [20, 22, 23] which although often seen in frustrated or low-dimensional magnetic systems have not yet been explained [20]. A recent proposed explanation for these apparent persistent spin dynamics in terms of quantum diffusion of muons suggested for $Dy_2Ti_2O_7$ [24] is untenable here (and likely in that case as well as we would expect similar muon diffusion behaviour in the two systems). If muons were mobile in $Yb_2Ti_2O_7$, then they would move between different possible magnetically inequivalent sites which would broaden all of the individual TF lines in Fig. 3 into one, which clearly does not occur. Furthermore, we can exclude a “muon impurity” effect in which the presence of the muon would locally destroy the magnetic behaviour, since our TF-μSR measurements are clearly sensitive to the transition which strongly affects the muon Knight shift.

$Yb_2Ti_2O_7$ exhibits a clear phase transition evidenced by specific heat measurements, however the ground state is not magnetically ordered. This leaves the nature of the low temperature state unresolved, although we do know that it involves a change of the local spin susceptibility and/or hyperfine coupling. This behavior recalls that of the moderate heavy fermion system URu_2Si_2 which has thermodynamic phase transition at 17.5 K to a so-called “hidden-order” state [25] without magnetic order, whose order parameter remained unknown for more than 20 years of detailed study. In the case of URu_2Si_2, recent studies [26–28] indicate the phase transition originates from a change in the hybridization between the localized electronic states associated with the uranium atoms and the conduction band, as it enters the heavy fermion state. While such a mechanism could not occur in insulating $Yb_2Ti_2O_7$, we are still left with a thermodynamic phase transition with an unidentified order parameter. Numerous exotic ground states have been proposed [29] for spin-1/2 pyrochlore systems including quantum spin liquid (QSL) and Coulomb ferromagnet in addition to antiferromagnetic and ferromagnetic order. Another possibility which could be considered is a valence bond solid (VBS). Of these states, the QSL and VBS would have no static magnetic moments consistent, with our results. However, it is unclear whether or how the known Hamiltonian for $Yb_2Ti_2O_7$ could give rise to either of these states. Which of these phases or perhaps other more exotic states is realized in $Yb_2Ti_2O_7$ remains to be seen.

Research at McMaster University and University of Waterloo is supported by NSERC while research at Columbia is supported by the US NSF PIRE (OISE-0968226) and DMR- 1105961 projects. We appreciate the technical support of Dr. B. Hitti and Dr. A. Dabkowski and the TRIUMF Centre for Molecular and Materials Science. This work is supported in part by the Canada Research Chair program (M.J.P.G., Tier 1) and by the Perimeter Institute for Theoretical Physics through Industry Canada and by the Province of Ontario through the Ministry of Economic Development & Innovation.

---

* dortenrm@mcmaster.ca

[1] J.S. Gardner, M.J.P. Gingras and J.E. Greedan. Rev. Mod. Phys. **82**, 53107 (2010).

[2] C. Castelnovo, R. Moessner and S.L. Sondhi. Nat. Lett. **451**, 4245 (2008).

[3] R. Applegate, N. R. Hayre, R. R. P. Singh, T. Lin, A. G. R. Day and M. J. P. Gingras, Phys. Rev. Lett. **109**, 097205 (2012).

[4] L.-J. Chang, S. Onoda, Y. Su, Y.-J. Kao, K.-D. Tsuei, Y. Yasui, K. Kakurai, and M.R. Lees. Nat. Comm. **3**, 992 (2012).

[5] Y. Yasui, M. Soda, S. Iikubo, M. Ito, M. Sato, N. Hamaguchi, T. Matsusshita, N. Wada, T. Takeuchi, N. Aso and K. Kakurai. J. Phys. Soc. Japan. **72**, 11 (2003).

[6] J.A. Hodges, P. Bonville, A. Forget, A. Yaouanc, P. Dalmas de Réotier, G. André, M. Rams, K. Królas, C. Ritter, P.C.M. Grubbens, C.T. Kaiser, P.J.C. King and C. Baines. Phys. Rev. Lett. **88**, 077204 (2008).

[7] K.A. Ross, L.R. Yaraskavitch, M. Laver, J.S. Gardner, J.A. Quilliam, S. Meng, J.B. Kycia, D.K. Singh, Th. Proffen, H.A. Dabkowska and B.D. Gaulin. Phys. Rev. B **84**, 174442 (2011).

[8] J.S. Gardner, G. Ehlers, N. Rosov, R.W. Erwin and C. Petrovic. Phys. Rev. B **70**, 180404 (2004).

[9] K.A. Ross, J.P.C. Ruff, C.P. Adams, J.S. Gardner, H.A. Dabkowska, Y. Qiu, J.R.D. Copley and B.D. Gaulin. Phys. Rev. Lett. **103**, 227202 (2009).

[10] K.A. Ross, L. Savary, B.D. Gaulin and L. Balents. Phys. Rev. X **1**, 021002 (2011).

[11] N. R. Hayre, K. A. Ross, R. Applegate, T. Lin, R. R. P. Singh, B. D. Gaulin and M. J. P. Gingras, arXiv:1211.5934, (2012).

[12] P. Bonville, J.A. Hodges, E. Bertin, J.Ph. Bouchaud, P. Dalmas de Réotier, L.-P. Regnault, H.M. Ronnow, J.-P. Sanchez, S. Sosin and A. Yaouanc. Hyper. Inter. **156/157**, 103−111 (2004).

[13] P. Dalmas de Réotier, V. Glazkov, C. Martin, A. Yaouanc, P.C.M. Gubbens, S. Sakarya, P. Bonville, A. Amato, C. Baines and P.J.C. King. Physica B. **374375**, 145-147 (2006).

[14] H. Takatsu, H. Kadowaki, T.J. Sato, J.W. Lynn, Y. Tabata, T. Yamazaki, and K. Matsuhira, Journal of Physics: Condensed Matter **24**, 052201 (2012).

[15] K.A. Ross, Th. Proffen, H.A. Dabkowska, J.A. Quilliam, L.R. Yaraskavitch, J.B. Kycia and B.D. Gaulin. Phys. Rev. B. **86** 174424 (2012).

[16] A. Yaouanc, P. Dalmas de Réotier, C. Martin and V. Glazkov. Phys. Rev. B. **84**, 172408 (2011).

[17] *Springer Handbook of Crystal Growth*, Chap. 12. H. Dabkowska, A. Dabkowski (Springer, Verlag Berlin Heidelberg) (2010).

[18] S.T. Bramwell, M.N. Field, M.J. Harris and I.P. Parkin. J. Phys. Condens. Matter **12** 483 (2000).

[19] J.A. Hodges, P. Bonville, A. Forget, M. Rams, K. Królas and G. Dhalenne. J. Phys. Condens. Matter **13** 9301 (2001).

[20] S.R. Dunsiger, A.A. Aczel, C. Arguello, H. Dabkowska, M.-H. Du, T. Goko, B. Javanparast, T. Lin, F.L. Ning, H.M.L. Noad, D.J. Singh, T.J. Williams, Y.J. Uemura, M.J.P. Gingras and G.M. Luke. Phys. Rev. Lett. **107**, 207207 (2011).

[21] P. Dalmas de Réotier, A. Yaouanc, L. Keller, A. Cervellino, B. Roessli, C. Baines, A. Forget, C. Vaju, P.C.M. Grubbens, A. Amato and P.J.C. King. Phys. Rev. Lett. **96**, 127202 (2006).

[22] Y.J. Uemura A. Keren, K. Kojima, L.P. Le, G.M. Luke, W.D. Wu, Y. Ajiro, T. Asano, Y. Kuriyama, M. Mekata, H. Kikuchi and K. Kakurai. Phys. Rev. Lett. **73**, 3306 (1994).

[23] P.A. McClarty, J.N. Cosman, A.G. Del Maestro and M.J.P. Gingras. J. Phys. Condens. Matter. **23**, 164216 (2011).

[24] P. Quemerais, P. McClarty and R. Moessner. Phys. Rev. Lett. **109**, 127601 (2012).

[25] J.A. Mydosh, P.M. Oppeneer. Mod. Phys. Rev. **83**, (2011).

[26] C. R. Wiebe, J. A. Janik, G. J. MacDougall, G. M. Luke, J. D. Garrett, H. D. Zhou, Y.-J. Jo, L. Balicas, Y. Qiu, J. R. D. Copley, Z. Yamani, and W. J. L. Buyers, Nature Physics **3**, 91–95 (2007).

[27] U. Nagel, T. Room, T. Uleksin, R. P. S. M. Lobo, P. Lejay, C. C. Homes, J. Hall, A. W. Kinross, S. Purdy, T. J. Williams, G. M. Luke and T. Timusk, Proc. Nat. Acad. Sci. **109**, 19161 (2012).

[28] A. R. Schmidt, M. H. Hamidian, P. Wahl, F. Meier, A. V. Balatsky, T. J. Williams, G. M. Luke and J. C. Davis, Nature **465**, 570 (2010).

[29] L. Savary and L. Balents, Phys. Rev. Lett. **108**, 037202 (2012).